



250 Chester Street  
 Painesville, Ohio 44077  
 Phone: 866-GO-AVERY (866-462-8379)  
 Fax: 888-358-4469  
 email: psa.tape@averydennison.com  
 URL: tapes.averydennison.com

**TEST REPORT**

PRODUCT: FT A902  
 SUPPORT: FLOCK  
 SUBSTRATE: PP  
 STD CERT NO.: 230926 - 0714




**GMW 16875 TYPE II-CYCLE-D**  
 OEM Rev Date: Jan 13

Performance Requirements of Anti-Squeak, Itch, Rattle Fiber Tape  
 Type IA material is a flocked fabric or felt tape coated with a permanent acrylic PSA not exposed to UV  
 Initial

**TAPE REQUIREMENTS:**

SECTION:	ISO 8510-2	Specification	Results	Status
Initial RT		900 N / m	39.3	Pass
SECTION: <b>Peel Adhesion</b>	ISO 8510-2	Specification	Results	Status
Aged, 72 hrs @ RT		280 N / m	682.6	Pass
Humidity, 24 hrs @ 38°C / 95% RH		280 N / m	959.1	Pass
Aged, 168 hrs @ 70°C		280 N / m	898.5	Pass
GMW 14124 CYCLE D		280 N / m	879.7	Pass
24 hrs @ 38°C / 100% RH				
4 hrs @ 85°C				
3 hrs @ RT				
17 hrs @ 85°C				
168 hrs @ 70°C				
4 hrs @ -30C				
100 hrs @ 70°C				
SECTION: <b>Shear Strength, MD</b>	ASTM D1000	Specification	Results	Status
4 hrs @ -18°C		2500 N / m	8994.6	Pass
24 hrs @ 60°C		2500 N / m	6228.2	Pass
SECTION: <b>Taber Abrasion*</b>	GMW3208	Specification	Results	Status
500 Cycles CS-10,0.5 kg Load		No Wear Thru to Fabric Backing	Worn But Not Thru	Pass
SECTION: <b>Flammability</b>	GMW3232	Specification	Results	Status
Initial, Component		100 mm / min	< B 25	Pass
SECTION: <b>Xenon Weatherometer*</b>	GMW14162	Specification	Results	Status
Not Applicable		No Degradation, Stiffening, Bleaching or Objectionable Color	Not Applicable	NA
SECTION: <b>Odor*</b>	GMW3205	Specification	Results	Status
Wet Condition, Coding A - 24 hrs @ 70°C, Deionized Water		6 Min Rating	Not Tested	NT
Dry Condition, Coding B - 24 hrs @ 70°C			Not Tested	NT
High Temp Condition - 24 hrs @ 105°C			Not Tested	NT
SECTION: <b>VOC*</b>	GMW15634	Specification	Results	Status
Per GMW 16853		6 mg	Not Tested	NA
SECTION: <b>Gravimetric Fogging</b>	GMW3235 Method B	Specification	Results	Status
18 hrs @ 100°C, 21°C Cooling, 24 hr RT Desiccant		2 mg	1.2	Pass

CERTIFIED BY:

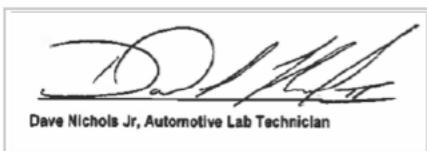

ISSUE DATE: 1-1-24

Materials tested to OEM requirements @ 72°F +/- 2°F and 50% RH +/- 5%. Test uncertainty and minor exclusions are available online or upon request.

This certificate or report shall not be reproduced except in full, without the written approval of the Avery Dennison® Performance Tapes.

Status opinion based upon measurements obtained by personnel with appropriate training and professional experience.

This laboratory is not accredited for the calibrations or tests marked \*.